

**Submission date:** 08-May-2023 07:16AM (UTC+0700)

**Submission ID:** 2086880385

File name: Conference-ICAST-ES-JatrophaOil\_2023SCITEPRESS\_1.pdf (449.4K)

Word count: 2855

**Character count:** 14708

# Development and Characterization of Jatropha Oil as Innovative Bio-sourced Phase Change Material for Thermal Energy Storage

Made Rasta<sup>1</sup><sup>1</sup><sup>1</sup><sup>0</sup><sup>a</sup>, Nyoman Suamir<sup>1</sup><sup>1</sup><sup>0</sup><sup>b</sup>, Wayan Adi Subagia<sup>1</sup><sup>0</sup><sup>c</sup>, Adi Winarta<sup>1</sup>, 2 Ketut Bangse<sup>1</sup><sup>0</sup><sup>d</sup> and Gusti Ketut Puja<sup>2</sup><sup>0</sup><sup>e</sup>

<sup>1</sup>Mechanical Engineering Department, Bali State Polytechnic, Bali-80364, Indonesia <sup>2</sup>Mechanical Engineering Department, Sanata Dharma University, Yogyakarta-55002, Indonesia

Keywords:

Jatropha Oil, Bio-phase Change Material, Thermal Energy Storage.

Abstract:

Thermal energy storage (TES) using phase change materials (PCM) is very promising to meet future energy needs because of its high storage capacity and low cost. This study aims to develop Jatropha oil as a new candidate for solid-liquid latent heat energy storage for cold storage applications. The characteristics of Jatropha oil as a candidate for PCM were tested experimentally using T-history methods. The test results show that Jatropha oil as a PCM candidate does not undergo super-cooling or super-cooling is very small compared to tap water and mineral water of 10 K and 15 K. The phase transition temperature of Jatropha oil ranges from -14 °C to -16 °C, lower than with tap freezing point and mineral water at 0 °C. Thus, the candidate PCM has good thermal properties that can meet the thermal energy storage requirements for cold storage applications.

# 1 INTRODUCTION

Along with the increase in the economy and population development, the need for energy is increasing. Energy is a vital need in development. Energy is still sourced from fossil fuels which can cause climate change and environmental degradation. Therefore, it is important to save energy and use new sources and renewable energy that are environmentally friendly for sustainable development. Energy storage (ES) systems 33 an important role in supporting energy security. Energy can be stored in electrical, mechanical and thermal energy.

One of the important ES systems for storing and retrieving energy for energy conversion systems is thermal energy storage (TES). The use of a TES system based on latent heat technology can save energy use from fossil fuels and conserve energy. TES helps rational use of thermal energy and has the

advantage that it allows the transfer of peak loads beyond peak loads, is significant in energy savings and mitigation of CO<sub>2</sub> that causes pollution to the env<sub>7</sub> nment.

Latent heat thermal energy storage (LHTES) is an attractive technique because it can provide a higher energy storage density than conventional TES systems. Has the ability to store the heat of fusion at a constant (relatively constant) temperature corresponding to the phase transition temperature of the

One of the typical applications of PCM is for the storage of solar thermal energy which is considered the most abundant renewable energy. Utilization of PCM for TES can overcome the intermittency of solar energy, thus providing a better solution to rationalize the utilization of solar thermal energy, compared to the sensible heat TES system.

obtain sustainable energy utilization. ES using

ES is a promising power management method to

https://orcid.org/0000-0002-9610-3738

https://orcid.org/0000-0003-0594-7511

https://orcid.org/0000-0001-9261-3549

do https://orcid.org/0000-0003-0220-056X

https://orcid.org/0000-0002-6025-3865

716

sta, M., Suamir, N., Subagia, W., Winarta, A., Bangse, K. and Puja, G.

4 elopment and Characterization of Jatropha Oil as Innovative Bio-sourced Phase Change Material for Thermal Energy Storage

OOI: 10.5220/0010952000003260

In Proceedings of the 4th International Conference on Applied Science and Technology on Engineering Science (iCAST-ES 2021), pages 716-720

ISBN: 978-989-758-615-6; ISSN: 2975-8246

Copyright © 2023 by SCITEPRESS - Science and Technology Publications, Lda. Under CC license (CC BY-NC-ND 4.0)

LHTES is currently receiving a lot of attention to reduce grid energy requirements.

TES schemes using PCM are categorized into 38 anic, inorganic and organic-inorganic mixtures. Organic PCMs, such as paraffin and fatty acids, have little super-cooling properties (no super-cooling occurs) because they have self-nucleation but lower thermal conductivity and higher cost. Inorganic PCMs, such as hydrated salts, are readily available and less expensive, but occurs phase separation, and corrosive (Rasta and Suamir, 2019). Therefore, it is important to select the optimal PCM in a given app 30 tion to meet operating and cost requirements.

The main problem of TES technology is developing effective PCM for energy storage (Wang & Lu, 2013). The main criteria in determining the selection of PCM material types for TES applications are to have a phase change 40 perature in the practical application range, have high latent heat and good thermal conductivity, as they involve the energy storage and thermal stability characteristics of the PC

By far the most famous PCM is water because it has good thermal properties, but has the disadvanta of high super-cooling (Rasta and Suamir, 2018). In this study, Jatropha oil was developed as a PCM material. Oil is a complex fatty acid/fatty acid ester. Oils or fatty acids are a new class of organic PCM materials and the thermal data available in the literatur are still limited (Aydin & Okutan, 2011). Oils or fatty acids are derivatives of materials easily found in nature and are labelled as bio-based ingredients (Cellata, et al., 2015; Sharma, et al., 2015). Another advantage is the still regetable oils are available continuously (Sharma, et al., 2014; Fauzi, et al., 2015; Suamir, et al., 2019).

Given the complexities of LHTES problems, developing an expectation of the complexities of LHTES problems, developing an expectation of the complexities of the complex transfer of the complex transf

### 2 MATERIAL AND METHOD

The material used as Latent Heat Thermal Energy Storage in this research is Jatropha oil. Jatropha oil was chosen because of its sufficient availability in the field and cultivated by farmers to increase their income. The Jatropha oil tested here has undergone a hydrolysis process. Jatropha oil contains various fatty

acids, both saturated and unsaturated fatty acids (PUFA).

The thermal properties of Jatropha oil will be compared with the thermal properties of tap water and mineral water. Water is an excellent PCM material, but has the disadvantage of high super-cooling and a freezing point of 0 °C. The results of the Jatropha oil test will be compared with water, to explain the characteristics of Jatropha oil.




Figure 1: Schematic diagram of the experimental test equipment T-history method (Rasta, et al., 2016a).

Figure 1 shows that the prospective PCM Jatropha oil in various volumes is put into a glass tube 3 d immersed in a water bath as a cooling medium. The cooling medium is a mixture of 40% (volume) polypropy! 9 e glycol with tap water. The cooling medium is circulat 6 by pump through the evaporator of the system. The temperature of the cooling medium can be as low as -25 °C. However, 9 or testing, the temperature of the cooling medium was maintained stable at -20 °C by using a digital thermostat with an accuracy of ±0.2 °C.

The data recording system shown in Figure 1 is equipped with a data acquisition module and a computer for recording or disp by systems. The data acquisition module utilizes the Data scan 7000 series from MSL (Measuring Systems Ltd) which includes the Data scan 7320 measurement processor and the 7020 expansion module. Type T thermocouples are used to measure the temperature of the PCM can 6 at each cooling medium. The thermocouple has a temperature measurement rable of -250 °C to 350 °C with an error of ± 0.5 °C. The thermocouple was calibrated using a water bath calibration and the uncertainty of the thermometer precision was ± 0.04 °C. In the test temperature range is -25 °C to 50 °C (Rasta, et al., 2016b).

#### 3 RESULT AND DISCUSSION

Super-cooling degree is an important parameter in LHTES technology using PCM. Figures 2 and 3 show

that tap water and mineral water 39 we high supercooling, namely 10 K and 15 K. Supe 11 oling is a condition that indicates the presence of tap water and mineral water still in liquid form below the freezing point of 0 °C. A LHTES tet 3 nology with high supercooling, will result in a much lower evaporation temperature required when applied in the cooling system. Thus will reduce the performance of the system. In addition, before tat 3 water and mineral water freeze, the energy stored is only in the form of sensible heat, causing a very small energy 19 rage

capacity. In order for tap water and minerals to store energy in the form of latent heat, more energy is

needed to change the state from liquid to solid. The greater energy requirements in PCM technology are in direct conflict with thermal energy storage

technology. So high super-cooling is a disadvantage

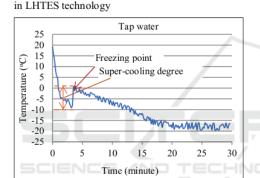


Figure 2: Cooling process and super-cooling tap water.




Figure 3: Cooling process and super-cooling mineral water.




Figure 4: Cooling process and Jatropha oil freezing point for sample 4 ml.




Figure 5: Cooling process and Jatropha oil freezing point for sample 8 ml.




Figure 6: Cooling process and Jatropha oil freezing point for sample 12 ml.




Figure 7: Cooling process and Jatropha oil freezing point for sample 16 ml.




Figure 8: Cooling process and Jatropha oil freezing point for sample 20 ml.

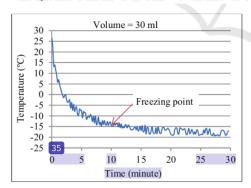


Figure 9: Cooling process and Jatropha oil freezing point for sample 30 ml.




Figure 10: Cooling process and Jatropha oil freezing point for sample 40 ml.

Table 1: Thermal energy storages properties of tap water, mineral water and Jatropha oil.

	Cooling process	
Samples	Freezing	Super-cooling
(Volume, ml)	temperature	degree
	(°C)	(K)
Tap water, 20 ml	0	10
Mineral water, 20 ml	0	15
Jatropha oil, 4 ml	14	0
Jatropha oil, 8 ml	14	0
Jatropha oil, 12 ml	15	0
Jatropha oil, 16 ml	15	0
Jatropha oil, 20 ml	15	0
Jatropha oil, 30 ml	16	0
Jatropha oil, 40 ml	16	

Figures 4-10 shows the cooling process of each volume variation of the Jatrop 2 oil sample developed as PCM. The test results of the T-history method show that in the early stages of 24 cooling process, there is a very rapid decrease in temperature to the initial limit of the transition phase temperature process. At the beginning of the phase transition process until it ends there is no significant or constant temperature change. When a phase transition occurs from the beginning to the end, this is where the storage of latent heat energy occurs. After that the freezing process takes place, the temperature decreases towards the final test temperature setting.

Overall, all samples developed with different volume f 23 ions of Jatropha oil are summarized in Table 1. The freezing 32 ht of the PCM candidate developed is lower than that of tap water and 7 neral water. The freezing point of Jatropha oil in various volumes of 4 ml, 8 ml, 12 ml, 16 ml, 20 m 280 ml and 40 ml, ranged from -14 °C to -16 °C. The results showed that increasing the volume of the sample tested did not significantly affect the change in freezing point. Thus, the advantages of Jatropha oil

4

do not occur super-cooling, have stable properti 36 are not corrosive and environmentally friendly. These properties make Jatropha 12 a potential PCM material for energy storage for latent heat thermal energy storage applications in low temperature refrigeration systems below 0 °C, compared to water (tap water and mineral water).

#### 4 CONCLUSIONS

An investigation of Jatropha oil as a candidate for the development of a new 17 ase change material (PCM) has been carried out. T-history thermal analysis was applied in the investigation and it was found that Jatropha oil has a phase transition temperature or freezing po 17 ranging from -14 °C to -16 °C. The results of the investigation also found that the candidate PCM under test conditions had a minimum or even none (negligible) super-cooling level. In addition, Jatropha oil has a continuous supply, is noncorrosive and non-toxic. Meanwhile, tap water and mineral water have high super-cooling, which are 10 K and 15 K, respectively, with a freezing point or phase transition temperature of 0 °C. This makes Jatropha oil applicable as a new PCM for cold storage applications below 0 °C.

## 22

# ACKNOWLEDGEMENTS

8

The authors would like to thank the financial support received from the Ministry of Education, Culture, Research, and Technology of the Republic of Indonesia. This fee is degreed to the Bali State Polytechnic DIPA Number: SP DIPA-023.18.2.677608/2021 dated November 23, 2020. which has been submitted to the head of the research as stated in the DIPA Fund Research Implementation Agreement Letter No.: 887/PL8/PG/2021, April 6, 2021.

#### REFERENCES

5

Aydın, A.A., Okutan, H. (2011). High-chain fatty acid esters of myristyl alcohol with even carbon number: Novel organic phase change materials for thermal energy storage-1. Solar Energy Materials and Solar Cells 95, 2752-2762.

Aydın, A.A., Okutan, H. (2011). High-chain fatty acid esters of myristyl alcohol with odd carbon number: Novel organic phase change materials for thermal energy storage-2. Solar Energy Materials and Solar Cells 95, 117-2423.

Cellata, K., Beyhana, B., Güngörb, C., Konukluc, Y., Karahand, O., Dündare, C., Paksoya, H. (2015). Thermal enhancement of concrete by adding bio-based fatty acids as phase change materials. Energy and 13 Building 106, 156-163.

Fabiani, C., Pisello, A.L., Barbaneraa, M., Cabeza, L.F. (2020). Palm oil-based bio-PCM for energy efficient building applications: Multipurpose thermal investigation and life cycle assessment. Journal of Energy Storage 28 (2020) 101129

Fauzi, H., Hendrik, S.C., Metselaar, Mahlia, T.M.I, Silakhori, M., Chyuan-Ong, H. (2015). Thermal characteristic reliability of fatty acid binary mixtures as phase change materials (PCMs) for thermal energy storage applications. Applied Thermal Engineering 80, 127-131

Rasta, I.M., Suamir, I.N. (2018). The role of vegetable oil in water based phase change materials for medium temperature refrigeration. Journal of Energy Storage 12, 15, 368-378.

Rasta, I.M., Suamir, I.N. (2019). Study on Thermal Properties of Bio-PCM Candidates in Comparison with Propylene Glycol and Salt Based PCM for sub-Zero Energy Storage Applications. IOP Conference Series: Ma 11 als Science and Engineering 494, 012024.

Rasta, I.M., Wardana, I.N.G., Hamidi, N., Sasongko, M.N. (2016a). The role of heterogeneous nucleation in water based Phase change material for medium temperature Refrigeration. ARPN journal of engineering and app 3rd sciences 11(2), 978-985.

Rasta, I.M., Wardana I.N.G., Hamidi, N., Sasongko M.N. (2016b). The Role of Soya Oil Ester in Water-Based PCM for Low Temperature Cool Energy Storage. Journal of Thermodynamics, Volume 2016, Article ID 14 5384640, 8 pages.

Suamir, I.N., Rasta, I.M., Sudirman, Tsamos, K.M. (2019).
 Development of Com-Oil Ester and Water Mixture Phase Change Materials for Food Refrigeration
 Applications. Energy Procedia 161, 198-206.

Sharma, A., Shukla, A., Chen, C.R., Wu, T.N. (2014).
 Development of phase change materials (PCMs) for low temperature energy storage applications.
 Sustainable Energy Technology Assessment 7, 17-21.

Sharma, R.K., Ganesan, P., Tyagi, V.V., Metselaar, H.S.C.,
 Sandaran, S.C. (2015). Developments in organic solid-liquid phase change materials and their applications in thermal energy storage. Energy Conversion and
 Management 95, 193-228.

Wang, H.Y., Lu, S.S. (2013). Study on thermal properties of phase change material by an optical DSC system.
Applied Thermal Engineering 60, 132-136.

Yingbo, C., Shifeng, Z., Qi, Z., Yusheng, C., Yufeng, Z. (2014). Composite phase change materials prepared by encapsuling paraffinin PVC macrocapsules. Thermochimica Acta 578, 10-14.

ORIG	INALIT\	Y REPORT
------	---------	----------

SIMILARITY INDEX

42%

**INTERNET SOURCES** 

**PUBLICATIONS** 

15%

STUDENT PAPERS

# **PRIMARY SOURCES**

1	repository.ub.ac.id
1	Internet Source

icast.isas.or.id

Internet Source

www.researchgate.net

Internet Source

repository.poliban.ac.id 4

Internet Source

3%

Submitted to University of Northumbria at 5 Newcastle

Student Paper

3%

www.hindawi.com

Internet Source

2%

coek.info Internet Source

2%

I.M. Rasta, I.N. Suamir. "The role of vegetable 8 oil in water based phase change materials for medium temperature refrigeration", Journal of Energy Storage, 2018

Publication

**7**%

9	www.arpnjournals.org Internet Source	2%
10	Meizhi He, Luwei Yang, Wenye Lin, Jiaxiang Chen, Xiang Mao, Zhenjun Ma. "Preparation, thermal characterization and examination of phase change materials (PCMs) enhanced by carbon-based nanoparticles for solar thermal energy storage", Journal of Energy Storage, 2019	2%
11	A. A. N. B. Mulawarman, I. M. Rasta, Putu Wijaya Sunu. "Characterization and Experimental Investigation of Glycerol and Propylene glycol in Water Solutions for cool Thermal Energy Storage", 2018 International Conference on Applied Science and Technology (iCAST), 2018 Publication	2%
12	Submitted to University Tun Hussein Onn Malaysia Student Paper	1%
13	ipco-co.com Internet Source	1 %
14	iopscience.iop.org Internet Source	1%
15	Rodrigo Canellas, Subba Digumarthy, Azadeh Tabari, Alexi Otrakji, Shaunagh McDermott,	1%

Efren J. Flores, Mannudeep Kalra. "Radiation dose reduction in chest dual-energy computed tomography: effect on image quality and diagnostic information", Radiologia Brasileira, 2018

Publication

16	www.scitepress.org Internet Source	1 %
17	bura.brunel.ac.uk Internet Source	1%
18	iieta.org Internet Source	1 %
19	ntnuopen.ntnu.no Internet Source	1%
20	spiral.imperial.ac.uk Internet Source	1%
21	worldwidescience.org Internet Source	1 %
22	Pin Jin Ong, Yihao Leow, Xiang Yun Debbie Soo, Ming Hui Chua et al. "Valorization of Spent coffee Grounds: A sustainable resource for Bio-based phase change materials for thermal energy storage", Waste Management, 2023 Publication	<1%

23	I. M. Rasta, I. N. G. Wardana, N. Hamidi, M. N. Sasongko. "The Role of Soya Oil Ester in Water-Based PCM for Low Temperature Cool Energy Storage", Journal of Thermodynamics, 2016 Publication	<1%
24	Submitted to University of Ulster Student Paper	<1%
25	www.porkenvironment.org Internet Source	<1%
26	Jefrey I. Kindangen, Octavianus H. Rogi, Pierre H. Gosal, Veronica A. Kumurur. "Attic ventilation and radiant heat barriers in naturally ventilated galvanized metal-Roofed buildings", Advances in Building Energy Research, 2022 Publication	<1%
27	www.pumpheat.eu Internet Source	<1%
28	Lisa Boussaba, Gilles Lefebvre. "Investigation of White Vaseline as an alternative Phase Change Material for Thermal Regulation of Physiological Birth Rooms", Journal of Building Engineering, 2021 Publication	<1%
29	Yingbo Chen, Shifeng Zhang, Qi Zhang,	<1%

Yusheng Chen, Yufeng Zhang. "Composite

# phase change materials prepared by encapsuling paraffin in PVC macrocapsules", Thermochimica Acta, 2014

Publication

30	daneshyari.com Internet Source	<1%
31	jit.ac.in Internet Source	<1%
32	oaktrust.library.tamu.edu Internet Source	<1%
33	scholar.ufs.ac.za Internet Source	<1%
34	theses.hal.science Internet Source	<1%
35	www.nrc.gov Internet Source	<1%
36	Alkan, C "Fatty acid/poly(methyl methacrylate) (PMMA) blends as form-stable phase change materials for latent heat thermal energy storage", Solar Energy, 200802 Publication	<1%
37	Hadi Fauzi, Hendrik S.C. Metselaar, T.M.I. Mahlia, Mahyar Silakhori. "Thermo-physical stability of fatty acid eutectic mixtures subjected to accelerated aging for thermal	<1%

# energy storage (TES) application", Applied Thermal Engineering, 2014

Publication

38

Sharma, R. K., P. Ganesan, and V. V. Tyagi. "Long-term thermal and chemical reliability study of different organic phase change materials for thermal energy storage applications", Journal of Thermal Analysis and Calorimetry, 2016.

<1%

Publication

39

I M Rasta, I N Suamir. "Study on Thermal Properties of Bio-PCM Candidates in Comparison with Propylene Glycol and Salt Based PCM for sub-Zero Energy Storage Applications", IOP Conference Series: Materials Science and Engineering, 2019

<1%

40

Sun, Zhiming, Weian Kong, Shuilin Zheng, and Ray L. Frost. "Study on preparation and thermal energy storage properties of binary paraffin blends/opal shape-stabilized phase change materials", Solar Energy Materials and Solar Cells, 2013.

<1%

Publication

Exclude quotes Off